

Flotation of copper-bearing shale in solutions of inorganic salts and organic reagents

Tomasz Ratajczak^{1,*}

¹Wroclaw University of Science and Technology, Faculty of Geoengineering, Mining and Geology, Wybrzeze Wyspianskiego 27, 50-370 Wroclaw


Abstract. Flotation data on copper-bearing shale in aqueous solutions of inorganic electrolytes (NaCl, Na₂SO₄, KPF₆, NH₄Cl) and organic reagents (ethylamine, propylamine) as frothers were presented and discussed. The relationships between shale flotation, surface tension of aqueous solution and foam height during bubbling with air in the flotation system were presented. It has been found that flotation of shale in the presence of inorganic salts the yield was directly proportional to the surface tension of the aqueous solution of salt and inversely proportional to the height of the foam. On the other hand, for organic reagents solutions (short chain amines), a reverse effect has been observed in relation to the inorganic compounds studied, that is the yield of copper-bearing shale flotation and the foam height were inversely proportional to the surface tension of the amine solution.

1 Introduction

Salt flotation relies on flotation in saline solutions [1, 2] without the presence of additional reagents. Salt flotation mechanism and results depend on the type, concentration and foaming properties of the saline solutions. Inorganic salts can replace organic frothers in flotation but not all inorganic salts are good frothers [1, 2, 3, 4, 5, 6, 7]. From these works it can be seen that the salts that raise or lower the surface tension can cause, respectively, an increase or decrease of flotation of naturally hydrophobic minerals. The aim of this work, which is based on flotation results of Smolska and Ratajczak [6] and Witan and Ratajczak [7], was to compare the influence of inorganic and organic reagents on flotation of naturally hydrophobic copper-bearing shale and to determine how the flotation results depend on foaming and surface tension of these reagents in aqueous solutions.

2 Flotation of copper-bearing shale in solutions of inorganic electrolytes

Flotation of copper-bearing shale, denoted by Drzymala et al. [8], as shale P, was carried out using a mono-bubble type Hallimond cell with a capacity of 200 cm³ and height of 36 cm. The investigations were carried out in distilled water and in the presence of aqueous solutions of NaCl, Na₂SO₄ at concentrations of 0.5 to 2 mol/dm³ and KPF₆ at concentrations of 0.05 to 0.25 mol/dm³, that is up to its solubility limit. More precise description of methodology of investigations is given in the works of Smolska and Ratajczak [6] and Smolska [9].

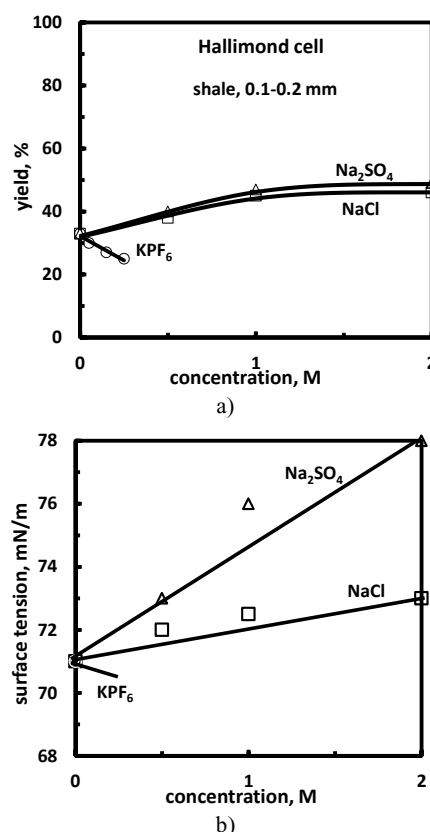

* Corresponding author: tomasz.ratajczak@pwr.edu.pl

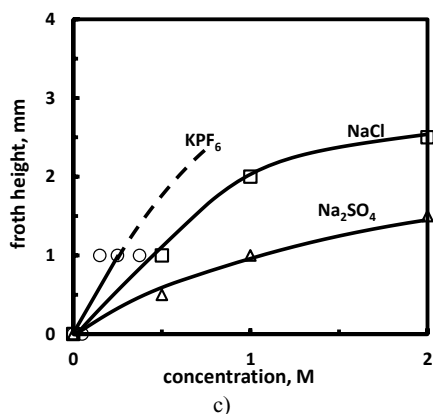


Fig. 1. Dependence of a) yield of flotation of copper-bearing shale [6], b) surface tension [6]; [2]; [10]; [11], c) foam height [6] on the concentration of the investigated salt solutions.

Smolska [9] investigated flotation and the height of foam during air bubbling through water containing salts that have different surface tension of aqueous solutions (Figure 1). Figure 1a shows that flotation yield decreases in the presence of KPF₆ and increases in the Na₂SO₄ and NaCl aqueous solutions. A comparison of yield with foam height and surface tension indicates that the yield increases in the same manner as surface tension and decreases with foam height.

3 Flotation of copper-bearing shale in solutions of organic reagents

To determine the influence of organic reagents on flotation, the tests were carried out in a Mechanobr flotation machine equipped with a 0.25 dm³ flotation cell. Reagents used for testing were ammonium chloride, as the first member of the normal short chain amines family and ethylamine as well as propylamine. For each flotation 30 g of -100 μm in size copper-bearing shale P was used. The time of flotation was 30 min. More details on methodology of flotation is given in the work of Witan and Ratajczak [7] and Witan [12].

Figure 2a shows the effect of concentration of ammonium chloride, ethylamine and propylamine on the yield of copper-bearing shale after 15 minutes of flotation. Figure 2b show the influence of concentration of the used frother surface tension change ($\Delta\gamma$) in relation to pure water while Fig. 2c the froth height. According to Fig. 2a, ammonium chloride makes the yield of shale slightly decreasing with a small rise in the froth height (Fig. 2c), while the surface tension increases (Fig. 2b). This agrees with the data obtained for inorganic salts show in Fig. 1. On the other hand, for ethylamine and propylamine, for which the surface tension decreases with increasing concentration of frother (Figure 2b), a slight increase in yield is observed with increasing height of flotation froth (Figure 2c).

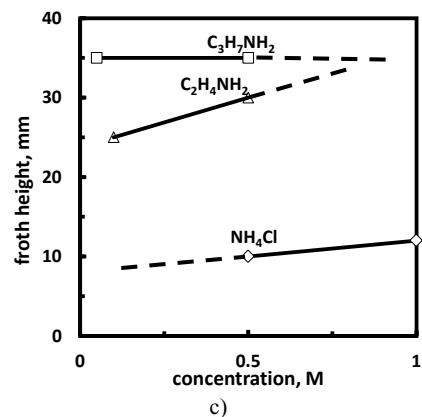
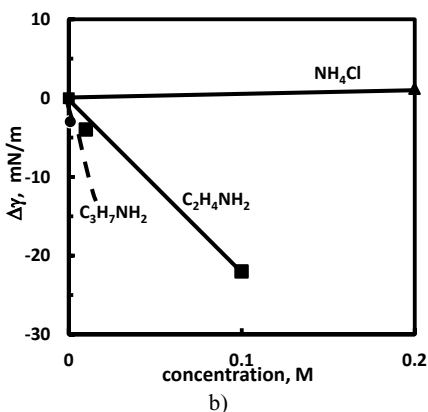
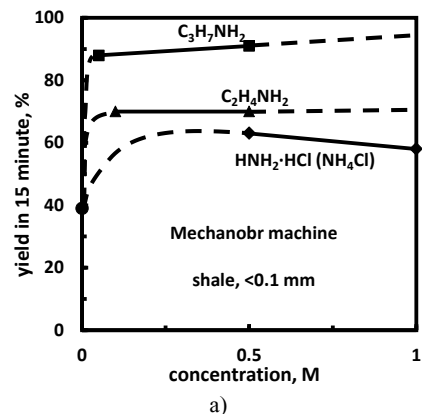


Fig. 2. Effect of concentration of ammonium chloride, ethylamine and propylamine on a) yield of copper-bearing shale after 15 minutes of flotation [7], b) surface tension of their solutions [13 (for NH₄Cl, at 25 °C); 14 (for C₂H₄NH₂ at 30 °C, 15 (for C₃H₇NH₂, at 25 °C), c) froth height after 5 minutes of shale flotation) [7].

4 Summary

The results of the studies confirm influence of inorganic and organic reagents on flotation of copper-bearing shale. It was found that in the case of increasing concentrations of NaCl and Na₂SO₄, shale yield increases while for KPF₆ it decreases. Thus, it is shown that the yield of salt flotation of shale depends on the concentration and type of salt. It increases with increasing surface tension of salt and decreases as surface tension of salt solution decreases. However, the foaming of the salt solution increases with lower surface tension of the salt, that is, as in the case of

organic frothers. Thus, the flotation of the shale in solutions of inorganic salts depends on the concentration, type of salt and foaming, and in turn on the surface tension of the salt.

Ammonium chloride behaves the same way as NaCl and other inorganic salts which increase surface tension. However, in the relations between yield, surface tension and froth height are different for organic reagents. Ethylamine and propylamine, for which the surface tension decreases with increasing concentration, make flotation better while froth height increases.

In addition, it can be noticed from Fig. 2 that the maximum yield of the flotation froth product in the presence of propylamine is higher than that in salmiac and ethylamine, indicating increasing collecting properties of amine with the increasing length of the hydrocarbon radical.

This work was financed by the Polish Statutory Research Grant 0401/0124/2016.

References

1. J. Laskowski, J. Colliery Guardian, **211**, 361-366, (1965)
2. T. Ratajczak, J. Drzymała, *Flotacja solna* (Oficyna Wydawnicza Politechniki Wrocławskiej, Wrocław, 2003)
3. R. J. Pugh, P. Weissenborn, O. Paulson, Int. J. Miner. Process., **51**, 125-138, (1997)
4. B. Grabowski, J. Drzymała, Annales UMCS Sectio AA, **LXIII**, **6**, 68-72, (2008)
5. M. Lipniarski, T. Ratajczak, J. Drzymała, *Weryfikacja hipotez o roli soli we flotacji na przykładzie węgla kamiennego w wodnych roztworach NaCl i KPF₆*, (III Polski Kongres Górniczy, Mineralurgia i wykorzystanie surowców mineralnych, Drzymała J., Kowalczyk P.B. (red.), 14-16 września 2015, Wrocław, WGGG PWr, 35–39, 2015)
6. M. Smólska, T. Ratajczak, *Flotacja solna łupka miedzionośnego we flotowniku Hallimonda* (WGGG PWr, Wrocław, 2017)
7. J. Witan, T. Ratajczak, *Stabilność piany flotacyjnej w obecności soli* (WGGG PWr, Wrocław, 2017)
8. J. Drzymała, P. Karwowski, K. Borowski, P. Pązik, P.B. Kowalczyk, *Próba klasyfikacji łupków Legnicko-Głogowskiego Okręgu Miedziowego na podstawie zawartości węglanów, mineralów ilastych, węgla organicznego oraz miedzi*, (in: Łupek miedzionośny III, Kowalczyk P.B., Drzymała J. (red.), WGGG PWr, Wrocław, 2017, doi: 10.5277/lupek1702, 2017)
9. M. Smólska, *Flotacja solna łupka miedzionośnego we flotowniku Hallimonda*. Praca dyplomowa, opiekun T. Ratajczak (WGGG PWr, Wrocław, praca niepublikowana, 2017)
10. J. Lyklema, *Fundamentals of interface and colloid science., Vol. 2, Fundamentals*, (Academic Press, London, 1995)
11. L. Ghosh, K.P. Das, D.K. Chattoraj, J. Coll. Int. Sci., **121**, **1**, 278-288, (1988)
12. J. Witan, *Stabilność piany flotacyjnej w obecności soli*. Praca dyplomowa, opiekun T. Ratajczak, (WGGG Politechniki Wrocławskiej, Wrocław, praca niepublikowana, 2017)
13. J. Lyklema, *Fundamentals of interface and colloid science. Vol. 3, Liquid-fluid interfaces* (Academic Press, London, 2000)
14. J. He, H. Liu, P. Shan, K. Zhang, Y. Qin, L. Liu, Chem. Eng. Sci., **141**, 330-341, (2016)
15. B. J. George, N. Pereira, M. A. Massum, S. D. Kolev, M. Ashokkumar, Ultrason. Sonochem., **15**, 151–156, (2008)