

# Strength Behaviour of Blended Self Cured Concrete made with Cement by partial replacement of Supplementary Cementitious Materials (SCM's)

*C Vivek Kumar<sup>1</sup>, MD Aiman Parvez<sup>2</sup> and T Srinivas<sup>3</sup>*

<sup>1</sup>Assistant Professor, Civil Engineering Department, GRIET, Hyderabad, Telangana, India.

<sup>2</sup>PG Student, Civil Engineering Department, GRIET, Hyderabad, Telangana, India.

<sup>3</sup>Professor, Civil Engineering Department, GRIET, Hyderabad, Telangana, India.

**Abstract.** At Present Water is the most essential material in the modern era. In general, Curing of concrete is retaining moisture in the concrete for the period of early ages precisely within 28 days of placing concrete, to improve anticipated properties. Appropriate curing of concrete is crucial to obtain extreme durability, especially if the concrete is exposed to serve conditions where the surface will be imperiled to excessive wear, assertive solutions, and severe environmental circumstances. Poor curing practices adversely affect the desirable properties of concrete which constitutes a major influence on the permeability of a given concrete. Unpredicted shrinkage and temperature cracks be able to diminish the strength, durability and serviceability properties of the concrete. The surface zone will be critically damaged by increased permeability expected to poor curing. The improvement of shrinkage in concrete is proportionate to the rate of moisture loss in concrete. When concrete is correctly cured, water preserved in concrete would facilitate continuous hydration and enhancement of enough compressive and tensile strength to withstand contraction stresses. The incessant development of strength reduces shrinkage and initial cracks or micro-cracks. As a part of this study, SCMs like Flyash (FA), Ground Granulated furnace Slag (GGBS), Silica Fume (SF). Concrete may be a mixture of cement, aggregates and water with / without suitable admixtures with self-curing agents and various proportions, which resulted in the early strength to reduce the autogenous shrinkage and increase in durability.

---

<sup>1</sup> Corresponding Author Email: [srinu.tummala@gmail.com](mailto:srinu.tummala@gmail.com)

## 1 INTRODUCTION

The effective methods to conserve the Mother Nature's resources and additionally minimize the environmental impact is to utilize Supplementary Cementitious Materials (SCMs) by superseding OPC partly or plenarily in concrete. "Since most of SCMs are pozzolanic in nature and hence they are subsidiary in incrementing later strength of concrete, blending of SCMs with cement has many advantages like preserving in cement, utilization of commercial by-products, enhancement of micro structural properties of concrete and reduces environmental impact through minimized greenhouse gases engenderment". Most of the SCMs are industrial by-products which are considered as waste and pollutants when dumped into land or thrown into dihydrogen monoxide bodies. "Therefore, Blending them in concrete becomes safe disposal method for them. Such SCMs are Flyash (FA), Ground Granulated furnace Slag (GGBS), Silica Fume (SF), concrete may be a mixture of cement, aggregates and water with or without suitable admixtures". to achieve desirable strength and other properties, curing is important.

Cement merging with SCMs with considerably higher specific surface than cement, and specifically irregular particles shapes with voids, results in inferior natural philosophy compared to normal cement. GGBS also show off the pozzolanic properties since it comprises low CaO as sustainable and eco-friendly substance which can be used in building industry. The main objective of the current study is to determine the mechanical properties the mechanical properties of compression test, split tensile test and flexural test for the blending of Supplementary Cementitious Materials.

## 2 MATERIAL PROPERTIES AND INVESTIGATIONS

To obtain specific experimental data which helps to understand the mechanical behaviour and optimum dosage of Polyethylene Glycol 400 and significance of utilization of Flyash, Ground Granulated furnace Slag and Silica Fume as partial replacement of river sand as fine aggregate, the experimental programme was taken up.

Cement 53-grade OPC confirming to IS: 12269-1987 was used in the investigation having a specific gravity of 3.21, specific surface area of 225 m<sup>2</sup>/g and initial and final setting times of cement were 35 minimum and 550 minimum respectively.

Fine aggregate as locally available river sand confirming to Zone-2 according to IS: 383-1970, was used as fine aggregate. The specific gravity and bulk density of sand were 2.62 and 1.5 g/cm<sup>3</sup> respectively. Coarse aggregate used is crushed granite angular aggregate passing through 20mm and retained on

4.75mm sieve. "The coarse aggregate used is conforms to IS 383-1970 and is tested as per IS 2386-1963 for its physical properties, its specific gravity 2.6, Bulk density (loose state) as 1450 kg/m<sup>3</sup> and (compacted state) as 1528 kg/m<sup>3</sup>. Potable water was used in the investigations for both mixing and curing of SCM specimens".

The Flyash obtained from Mettur Thermal Power Station having specific gravity of 2.17. and composition consisting of silica content as 63.99%, calcium oxide as 1.71%, magnesium oxide of 1.0%, pH as 10 and loss on ignition as 2.12%.

"GGBS blended concrete is significantly more resistant to the ingress of chloride ions in concrete apart from reduced permeability. GGBS was procured in JSW Steel Ltd, Karnataka mainly having SiO<sub>2</sub> as 35.20%, Al<sub>2</sub>O<sub>3</sub> as 19 % and CaO as 34.90 %".

Polyethylene Glycols (PEGs) of low molecular (400) used in the study. The chemicals were mixed with water thoroughly prior to mixing of water in concrete. "A polycarboxylate-type, new-generation high range water reducing admixture confirming to ASTM C494 was used as super plasticizer for improving the flow workability of mix with decreased water-cement ratio, These admixtures when they disperse in cement agglomerate significantly and reduce the viscosity of the paste forming a thin film around the cement particles".

Various dosages of "Flyash, GGBS and Silica fume has 65+25+15, 65+20+15, 65+25+10 and 65+20+15 of various mix proportions are determined, in which the optimum dosage of blended elements will arrived for M30 grade of concrete with super plasticizer and PEG 400 as 1% of the weight of the cement content". Though the specimens

Samples of M30 grade blended concrete beams made with optimum amount of Flyash, GGBS and Silica fume replacement were casted.

The "mix proportioning was done constructed on the approach of Indian Code for mix design for blending concrete M30 of binary, ternary and quaternary blended concretes made with optimum blends of fly ash (FA), Silica fume (SF) and Ground Granulated furnace Slag (GGBS). Numerous trial mixes are showed on number of blended concrete mixes made with the diverse possible combinations of Fly Ash (FA), Silica Fume (SF) and Ground Granulated furnace Slag (GGBS), were to progress several quaternary blended concrete mixes".

**Table 1.** Proportions of M30 Concrete

| S.No   | Material            | Quantity (kg/m <sup>3</sup> ) |
|--|---------------------|-------------------------------|
| 1.   | Cement              | 350                           |
| 2.   | Fine aggregate      | 744.25                        |
| 3.   | Coarse aggregate    | 1314.18                       |
| 4.   | Polyethylene Glycol | 2.28                          |
| 5.   | Super Plasticizer   | 3.5                           |
| 6.   | Water               | 175                           |
| 7.   | Water cement ratio  | 0.4                           |
| Cement: Fine Aggregate: Coarse Aggregate: w/c ratio = 1:2.12:3.75:0.40 |                     |                               |

As per clause 8.2.4.2 of “IS 456-2000, the maximum cement content is restricted to 450 kilograms per cubic metre of concrete. Later trial mixes, revised quantities in kg per cubic metre for grade (M30) blended concrete mix are reached without compromising the required strength property”.

The computed amount of OPC is 350 kg and it was separated to pozzolanic materials like Flyash (FA), Ground Granulated furnace Slag (GGBS), Silica Fume (SF) with various dosages arrived from the literature studies formulated in table 1.

**Table 2.** Mix Proportions of various trial mixes for M30 Concrete

| MIX (%)        | CEMENT | FLYASH | GGBS | SILICA FUME | C.A     | F.A     | S.P | WATER |
|----------------|--------|--------|------|-------------|---------|---------|-----|-------|
| M1 (100)       | 350    | --     | --   | --          | 1314.18 | 744.255 | 3.5 | 140   |
| M2 (65+25+15)  | 227.5  | 87.5   | 35   | --          | 1314.18 | 744.255 | 3.5 | 140   |
| M3 (65+25+15)  | 227.5  | --     | 87.5 | 35          | 1314.18 | 744.255 | 3.5 | 140   |
| M4 (65+25+15)  | 227.5  | 87.5   | --   | 35          | 1314.18 | 744.255 | 3.5 | 140   |
| M5 (65+20+15)  | 227.5  | 70     | 52.5 | --          | 1314.18 | 744.255 | 3.5 | 140   |
| M6 (65+20+15)  | 227.5  | --     | 70   | 52.5        | 1314.18 | 744.255 | 3.5 | 140   |
| M7 (65+20+15)  | 227.5  | 70     | --   | 52.5        | 1314.18 | 744.255 | 3.5 | 140   |
| M8 (65+25+10)  | 227.5  | 87.5   | --   | 35          | 1314.18 | 744.255 | 3.5 | 140   |
| M9 (65+25+10)  | 227.5  | 87.5   | 35   | --          | 1314.18 | 744.255 | 3.5 | 140   |
| M10 (65+25+10) | 227.5  | --     | 87.5 | 35          | 1314.18 | 744.255 | 3.5 | 140   |
| M11 (65+20+15) | 227.5  | 70     | --   | 52.5        | 1314.18 | 744.255 | 3.5 | 140   |
| M12 (65+20+15) | 227.5  | 70     | 52.5 | --          | 1314.18 | 744.255 | 3.5 | 140   |
| M13 (65+20+15) | 227.5  | 70     | --   | 52.5        | 1314.18 | 744.255 | 3.5 | 140   |

\*\*\* The Slump values for various mixes of SCM's with cement from M1 to M13 with addition of polyethylene glycol 400 as 1% as shown in figure 1.

### 3. RESULTS

Optimum dosage of Polyethylene Glycol (PEG 400) considering the weight loss, water retention capacity of self-cured concrete mixes made with SCM's calculated (in grams) as 17, 25 and 38 according to the curing time of 7, 14 and 28 days respectively. Comparing with normal cured concrete, it is 55, 78 and 92 grams “according to the curing time of 7, 14 and 28 days correspondingly, optimum dosage of PEG 400 can be further reduced to 0.5% for higher grades of self-cured concrete mixes”. “As per the result of slump cone values, it is concluded that the workability has been improved in the mix percentages 65%+25%+15% and slightly decreases as to the other mixes as shown in fig 1. In the mixes produced with Flyash and silica fume have improved the workability and higher strengths compared with the ratio of blending with GGBS and Flyash”.

Concrete cubes of size 150mm and cylinders of size 100 mm x100mm x500mm were casted with various proportions of Various dosages of Flyash, GGBS and Silica fume has 65+25+15, 65+20+15, 65+25+10 and 65+20+15 with replacement of cement for testing

compressive and split tensile strength of blended self-cured concrete.

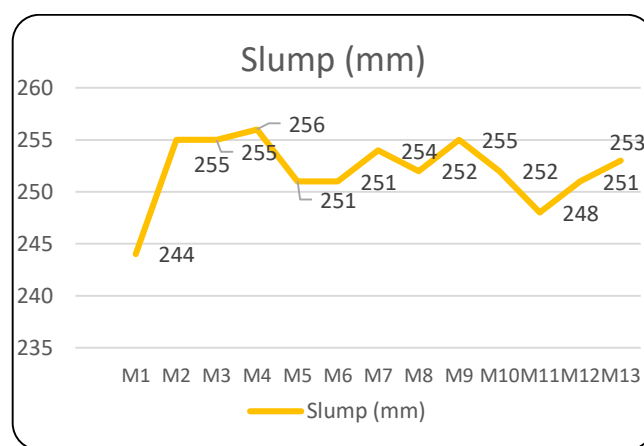


Fig 1. Slump values for M30 blended concrete of several mixes

Table 3. Compressive Strength of various trial mixes

| MIX (%) | Compressive Strength in MPa (M30) |         |         |
|---------|-----------------------------------|---------|---------|
|         | 7 days                            | 14 days | 28 days |
|         |                                   |         |         |

|     |       |       |       |
|-----|-------|-------|-------|
| M1  | 12.48 | 20.15 | 31.21 |
| M2  | 16.04 | 26.67 | 41.12 |
| M3  | 16.79 | 25.6  | 38.16 |
| M4  | 15.52 | 25.89 | 37.85 |
| M5  | 13.06 | 24.52 | 35.21 |
| M6  | 13.97 | 22.52 | 36.76 |
| M7  | 14.03 | 20.78 | 35.07 |
| M8  | 13.36 | 21.42 | 34.25 |
| M9  | 14.08 | 20.76 | 33.53 |
| M10 | 14.64 | 23.78 | 34.86 |
| M11 | 15.97 | 25.29 | 38.95 |
| M12 | 15.17 | 23.9  | 35.29 |
| M13 | 14.25 | 21.19 | 33.93 |

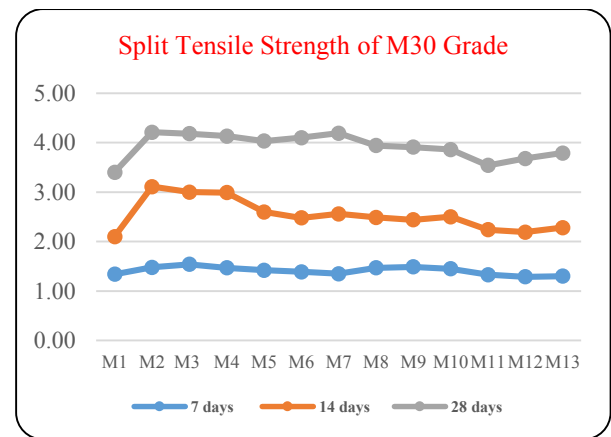


Fig 2. Graph displaying Split Tensile Strength of various mixes

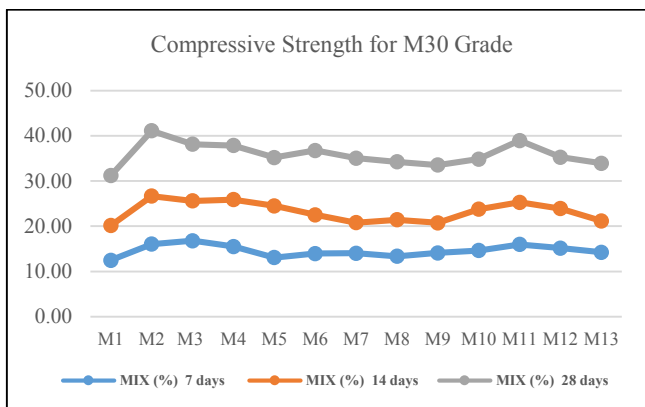


Fig 2. Graph displaying Compressive Strength of various mixes

Table 4. Split Tensile Strength of various trail mixes

| Mix % | Split Tensile Strength in MPa (M30) |         |         |
|-------|-------------------------------------|---------|---------|
|       | 7 days                              | 14 days | 28 days |
| M1    | 1.34                                | 2.1     | 3.40    |
| M2    | 1.48                                | 3.11    | 4.21    |
| M3    | 1.54                                | 3.0     | 4.18    |
| M4    | 1.47                                | 2.99    | 4.13    |
| M5    | 1.42                                | 2.6     | 4.03    |
| M6    | 1.39                                | 2.48    | 4.10    |
| M7    | 1.35                                | 2.56    | 4.19    |
| M8    | 1.47                                | 2.49    | 3.94    |
| M9    | 1.49                                | 2.44    | 3.91    |
| M10   | 1.45                                | 2.5     | 3.86    |
| M11   | 1.33                                | 2.24    | 3.54    |
| M12   | 1.29                                | 2.19    | 3.68    |
| M13   | 1.30                                | 2.28    | 3.79    |

#### 4. DISCUSSIONS

The concrete was cast as per Mix Design M30 grade (IS 10262:2009). The obtained concrete was tested for strength properties. “The different strength tests which includes compression test and split tensile test. The measurements of Polyethylene Glycol 400 were changed from 1% by weight of the concrete was utilized as self-relieving operator with that various doses of SNF fluctuated from 1% by weight of the solid to oneself restoring solid blend and contrasted the test outcome and the triple mixed self-restored concrete, from these final quantities, for various percentage replacement of cement by FA, SF, GGBS and their combinations are tried to optimize the quantities for binary, ternary and quaternary blended SCC mixes of grades considered”. The percentage replacements, their corresponding desired strengths are tabulated in Table-3. In Table-4, final optimal quantities of various grades of SCC mixes along with their total powder content and water / powder ratios are mentioned. “In Table-5, compressive strengths for various binary, ternary and quaternary blended optimal SCC mixes are tabulated, the performance of self-cured by PEG 400 applied to concrete is the greatest if 45 kg/m<sup>3</sup> Added water by means of 1 kg/m<sup>3</sup> PEG 400”.

Table 5. Strengths of optimally blended M30 grade concrete mixes

| Mix No   | Mix Designation (% by weight) | Strength Parameters in MPa |         |         |
|--|-------------------------------|----------------------------|---------|---------|
|  |                               | 7 days                     | 14 days | 28 days |
| Compressive Strength of M30 Blended Concrete   |                               |                            |         |         |
| M2   | 65%+25%+15%                   | 16.04                      | 26.67   | 41.12   |
| M6   | (65%+20%+15%                  | 13.97                      | 22.52   | 36.76   |
| M10  | 65%+25%+10%                   | 14.64                      | 23.78   | 34.86   |
| M11  | 65%+20%+15%                   | 15.97                      | 25.29   | 38.95   |
| Split Tensile Strength of M30 Blended Concrete |                               |                            |         |         |
| M2   | 65%+25%+15%                   | 1.48                       | 3.11    | 4.21    |
| M7   | (65%+20%+15%                  | 1.35                       | 2.56    | 4.19    |
| M8   | 65%+25%+10%                   | 1.47                       | 2.49    | 3.94    |
| M13  | 65%+20%+15%                   | 1.30                       | 2.28    | 3.79    |

## 5. CONCLUSIONS

Based on the experimental investigations and test results the following conclusions are documented as below-

1. The incorporation of polyethylene-glycol to concrete reduces water evaporation, which leads to an increase in water retention capacity of the concrete eventually leading to improved compressive strength. The adequacy of internal curing by methods for PEG 400 applied to concrete is higher when 45 kg/m<sup>3</sup> water is included by procedures for 1 kg/m<sup>3</sup> of self-curing concrete. The PEG 400 was more efficient than traditional curing concrete. The Performance of self-curing agent is basically influenced by the concrete material and the w/c proportion.
2. For development of high strength concrete mixes (M30), use of micro silica is compulsory due to its inherent high reactive property and micro-filler capacity.
3. This improvement in strength is due to incessant cement hydration is because of retained water presence and also due to the conversion of calcium hydroxide into calcium silicate hydrate (CSH) strengthening the interface aggregate-matrix transition zone which becomes less porous and more compact.
4. In development of high strength (M30) grade fly ash blended concrete mixes, both GGBS and Silica fume are required to be added to leverage the benefits of micro-filler capacity of micro silica and early strength attainment of metakaolin. Addition of silica fume (SF) to blended concrete mixes will enhance early hydration because of its high reactivity.
5. Optimally blended high strength grades M30 triple blended concrete mixes made of should be compacted 65%OPC+25%FA+10%GGBS yields both required workability and desired compressive strengths. From this observation, it can be understood that GGBS in blended concrete mixtures imparts high strength. So, it is evident that both Fly Ash and GGBS are required in blended concrete mixes made with low water/powder ratio.
6. The early age strength of concrete with GGBS was lower than the control concrete. However, as the curing period is extended, the strength increases. The reason is that the pozzolanic reaction is slow and the formation of calcium hydroxide requires time.
7. The compressive strength properties of concrete increases as the Flyash and GGBS content having 65%+25%+15% (M2,M3 and M4) having a higher compressive strength for mixes having 65%+20%+15% (M5,M6 and M7), 65%+25%+10% (M8,M9 and M10) increased up to an optimum point in 65%+20%+15% (M11, M12 and M13).

Hence it can be concluded that, there is an optimum level for the efficient use of GGBS content, which yields the highest strength in 65%+25%+15% (M2,M3 and M4). The optimum level of GGBS content for maximizing strengths is at about 30% of total binder content.

8. The split tensile strength properties of concrete increases as the Flyash and GGBS content having and gradual increase in mix proportions of 65%+25%+15%(M2,M3 and M4) having a higher compressive strength for mixes having a and slight decrease 65%+20%+15% (M5,M6 and M7), 65%+25%+10% (M8, M9 and M10) increased up to an optimum point in 65%+20%+15% (M11, M12 and M13). Hence it can be concluded that, there is an optimum level for the efficient use of GGBS content, which yields the highest strength in 65%+25%+15% (M2,M3 and M4).
9. Addition of silica fume in concrete, beyond 25% does not improve the early strength. And it can be concluded that, after certain limit, the silica fume, which can produce hydration reaction, but behaves filler modules It indicates that, GGBS cannot be used efficiently as a binder, but rather as filler in the concrete.

## References

1. Bentz D P and Stutzman P E (2006), "Curing, Hydration, and Microstructure of Cement Paste," ACI Materials Journal, 103 (5), pp.348-356.
2. Bilek B et al. (2002) "The possibility of self-curing concrete" Proceedings of Innovations and developments in concrete materials and construction." International Conference University of Dundee, UK. 9-11 September 2002.
3. Dhir R K, Hewlett P C, Dyer T D, "Mechanisms of water retention in cement pastes containing a self-curing agent" , Magazine of Concrete Research, Vol. No 50, Issue No 1, 1998, pp. 85-90.
4. Mangaiarkarasi, V, Damodarasamy S R, "Self-curing concrete today's and tomorrow's need of construction world", INCRAC & CT2005- Proceedings International Conference on Recent Advances in Concrete and Construction Technology. Vol.2 pp.233-245, December 2005, Chennai.
5. Hans W Reinhardt and Silvia Weber (1998), "Self-Cured High Performance Concrete" Journal of Materials in Civil Engineering, November 1998, pp.101-109.
6. Nirav R Kholia, Bonita A Vyas, T G Tank (2013), " Effect On Concrete By Different Curing Method and efficiency Of Curing Compounds," International Journal of Advanced Engineering Technology, Vol. IV, Issue II, April-June, 2013, pp.29-38.

7. ACI Committee 308R-01, 2008, “Guide to Curing Concrete”, American Concrete Institute, Farmington Hills, MI.
8. Wen-Chen Jau (2008) “Self-curing Concrete”, United States Patent Application Publication, Pub. No: U.S. 2008/0072799 A1, Published date: Mar. 27, 2008.
9. A S El-Dieb (2007) “Self-curing Concrete: Water Retention, hydration and moisture transport”, Construction and Building Materials, Vol. 21 (2007), pp. 1282-1287.
10. Tummala Suresh Kumar, Kosaraju Satyanarayana, Materials Today: Proceeding, 26 (2), 3228-3233, (2020).
11. V Srinivasa Reddy and R Nirmala, “Development of quaternary blended high-performance concrete made with high reactivity metakaolin”, International Journal of Engineering & Technology, Vol 7 (2.1), 2018, pp 79-83.
12. Satyanarayana, G.V.V., Saikiran, C.H, “ Effect on mechanical properties of M35 grade concrete by partial replacement of fine aggregate with copper slag”, IJITEE, **8** (12), pp 3759-3762.
13. Sateesh, N., Sampath Rao, P., Ravishanker, D.V., Satyanarayana, K., “*Effect of Moisture on GFRP Composite Materials*”, *Materials Today: Proceedings*, **2** (4-5), pp. 2902-2908, (2015).
14. Reddy, V.M., Manikanta, S, “Mechanical properties of fibre reinforced self compacting concrete using rice husk ash”, IJRTE, **8** (3), pp. 6412-6415, (2019).