

Bio-Mediated Sandy Soil Stabilization Using Urease Enzymatic Calcite Precipitation: A Sustainable Solution

¹V Srinivasa Reddy, ²K Hema Latha, ³Ravulaparathi Sudha Lahari, ⁴M V Seshagiri Rao

¹Professor of Civil Engineering, GRIET, Hyderabad, India.

²Assistant Professor of Civil Engineering, GRIET, Hyderabad, India.

³M.Tech (Structural Engineering), Department of Civil Engineering, GRIET, Hyderabad, India.

⁴Professor of Civil Engineering, CVR College of Engineering, Hyderabad, India.

Abstract- A recently developing bacteria based soil-stabilization technique inspired from microbially impelled calcite precipitation phenomena is verified for geo-technical applications. This phenomena make use of the metabolic mechanics of microorganisms to produce calcite precipitation all through soil matrix enhancing the soil's engineering properties. Unconfined compressive strength (UCS) and soil hydraulic conductivity or permeability is evaluated to validate the formation of mineral precipitates between and around soil grains. Due to metabolic process of bacteria calcite minerals are generated binding the soil particles together reducing the voids volume and diameter subsequently a dense microstructure is formed. This improvement of soil homogeneity reduces the hydraulic conductivity and increase the unconfined compression strength of bacteria-treated soil samples. From the results of experimental investigations it is confirmed that mineral precipitation biologically proves to be an effective and efficient method of soil stabilization in increasing the stiffness and permeability of soil samples considered for study.

1 Introduction

In the present study the two soil samples with fine and coarse particle size distribution were treated with *Sporosarcina pasteurii* bacteria to stimulate mineral precipitation by producing urease enzyme which catalyzes the urea hydrolysis forming CO₂ and NH₃. Due to high pH environment of produced ammonia, the soil matrix nearby converts to extremely alkaline and calcium ion from calcium nutrient source reacts with CO₂ to form calcium carbonate minerals which will ultimately binds the soil particles.

2 MICP Mechanism

Biological methodology for soil consolidation is a comparatively novel practise, so it is essential to collect further outcomes to mimic real situations before applying on a larger scale. In this study, bacteria- based consolidation method is developed by adding the microbial self-healing agent which is likely to improve the feature of density largely by bacteria prompted mineral precipitations (MICP). In the current study the designated spore-forming alkaliphilic calcite precipitating bacteria would decompose

urea to CO₃²⁻ which can react with Ca²⁺ to form CaCO₃ in alkaline environment. The MICP mechanism is ascribed to urea hydrolysis by the urease enzyme of bacteria into NH₃, and CO₃⁻ ions causing the formation of calcite minerals. So urease activity is responsible for the formation of crystal precipitates.

3 Choice of bacterial strain and cultivation media

For isolation, enrichment culture technique will be used to enrich calcite precipitating strains in Urea broth. After enrichment, distinct bacterial strains were obtained on Urea agar. Based on qualitative and quantitative screening for urease activity, an isolate possessing higher calcite formation and urease activities (μmhos/cm) is identified and selected for study. For enrichment, 1 ml or one gram of bacterial strain is added to urea broth and incubated at 37 °C for 48–72 h. After enrichment, the broth samples were serially diluted and plated on Urea agar (pH 9.4) containing urea (20 g/l), sodium bicarbonate (2.12 g/l), ammonia chloride (10 g/l), Nutrient broth (3.0 g/l), calcium chloride hydrate (25 g/l). Crystal precipitation in the form of colonies

will be appeared and selected for further growth in urea based nutrient broth. Standard gram staining procedure can also be conducted to identify the bacterial strains growth and formation of endospores. The selection of the most suitable bacteria for MICP is mostly based on higher carbonate precipitation yield of the ureolytic pathway. A spore forming alkaliphilic bacteria is chosen based on CaCO₃ precipitation yield. Bacterial decomposition of urea to produce mineralized calcium carbonate critically depends on urease activity.

4 Molecular identification of the isolate

The pure culture will be isolated and is kept continuously on nutrient agar slants. It forms irregular dry white colonies on nutrient agar plate. Whenever we require bacterial culture a single colony of strain is isolated and inoculated in a broth of nutrients and allowed to grow at a temperature of 37 degree celcius and on orbital shaker. 16S rRNA gene sequence analysis is carried out to get the dendrogram which depicts the hierarchical relations among the family of bacillus. The 16S RNA bacterial gene is sequenced and analysed for the feasibility to be used for the study.

5 Identification of bacteria growth characteristics

Bacteria selected is grown in different medium to understand the suitability of nutrients for optimum bacterial growth and subsequently calcite crystals. To assess the cell concentration an optical density test is conducted. Similarly serial dilution technique is used to find the cell count. Urease activity of the selected bacteria is tested in different medium of nutrients. Phenol-hypochlorite assay is conducted to determine the ammonia release concentration.

6 Urease activity

Quality of the urease activity of the bacteria can be found by inoculating the selected bacterial strain on urea agar tubes at 37 degree Celsius for 3 to 5 days. Tubes are checked every day so when colour changes to orange from red indicates superior urease activity of bacterial strain

Quantity of urease activity can be assessed using an electric conductivity test. Selected bacterial strain along with nutrients which has grown throughout the night is centrifuged to make cell pellets. These cell pellets are mixed with distilled water and urea nutrient is added to check the optical density OD₆₀₀ so that when the value of OD is 1 then conductivity test is carried out to determine cell

concentration. The conductance of light is recorded regularly until the desired cell count is obtained.

7 Bio-mineralization test

To calculate the amount of calcite crystal precipitation pure bacterial culture is inoculated n nutrients containing the urea and calcium chloride on agar tubes at suitable temperature for required days on the orbital shaker and centrifuged to make pellets out of it. These bacterial cell pellets are dried and weights are taken to quantify the dry calcite crystal precipitate.

Detection of calcium carbonate was also carried out using Fourier transform infrared spectroscopy (FTIR). The calcite mineral presence will be established by observing the curve peaks formed at 1000–1300 cm⁻¹ wave number.

8 Preparation of bacterial suspension

Selected spore-forming alkaliphilic calcite precipitating bacteria is first cultured in solid media (agar) are then transferred to nutrient broth (liquid media) which is sterile and kept in shaking incubator (to ensure uniform growth) for about 48 hrs. From this we would get the mother culture of the bacteria. Later, it will be diluted by serial dilution technique for different cell concentrations, so that it can be utilized in soil samples. Concentration of cells is measured by Haemocytometer and optical density is found by spectrophotometer analysis before adding bacteria to soil sample.

Additionally Calcium lactate can be used as Ca supplement for metabolic activity

9 Cell Concentrations

Various bacterial cell count used are 10³ cells/ml, 10⁴ cells/ml, 10⁵ cells/ml, 10⁶ cells/ml and 10⁷ cells/ml.

10 Nutrients Broth for cementation

It comprised essentially urea, sodium bicarbonate, ammonia chloride, calcium chloride hydrate (25 g/l)

11 Sand Samples

Two types of sand samples (Coarse sand: 4.75mm - 2.00mm IS Sieve and Fine sand: 0.425mm - 0.075mm IS Sieve) having different particle size distribution are used in this study. Samples are made free from roots, organic matter etc. by sanitation and was then oven dried. Specific gravity of sand is determined by IS: 2720– 1985 (Part 3).

The geotechnical properties are evaluated as shown below-

Table 1. The geotechnical properties of sand

Liquid limit	Non-plastic
Opt. moisture content	16 %
Sp. gravity	2.65
Maximum dry density	13.9 kN/m ³

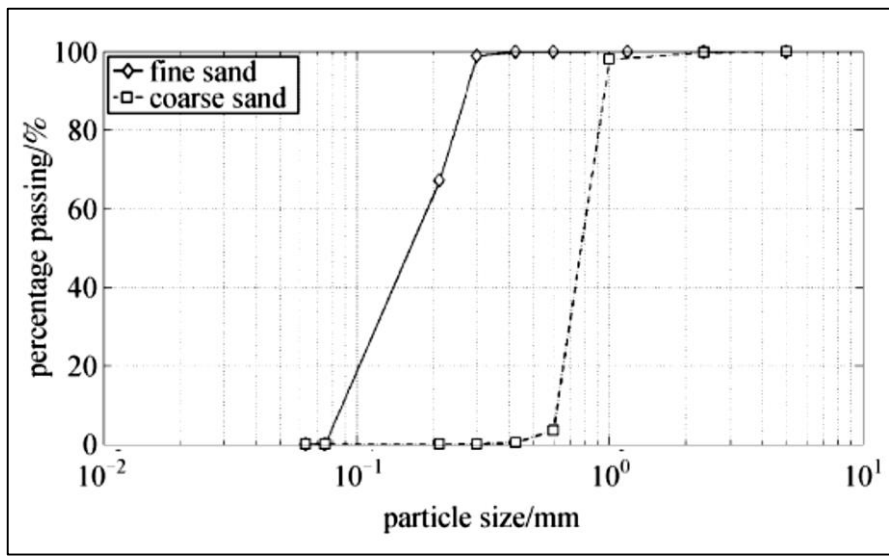


Fig. 1. Particle gradation Chart

12 Grain size distribution analysis

12.1 Sieve Analysis

Sieve analysis is carried out to assess the grain size distribution of sample as per IS: 2720– 1985(Part 4). The sample is put through various sieves. 4.25mm, 2mm, 1mm, 425 micron, 150 micron and 75 micron. A graph is drawn with percentage passing of particles versus the sieve size. Sample retained on each sieve is weighed. If the sample passing 75µm is more than 10% then hydrometer method can be used to grade the particles size of sample

12.2 Hydrometer analysis

Based on the nomogram given in IS: 2720– 1985 (Part 4), the diameter of the grains for different hydrometer readings are obtained. With the results obtained from sieve analysis and hydrometer method analysis, semi-log graph between grain size on x axis (log scale) and the percentage finer than the stated diameter as y axis.

12.3 Grade Curve

Grading curve shows the grain size distribution of sample considered. D_{60} , D_{30} , and D_{10} corresponds to grain size at which 60%, 30% and 10% fines are available are obtained from the curve. The curve is plotted with percentages of fines and the grain size on on y and x-axes respectively using data obtained from on the sieve analysis test

completed on given samples. D_{10} is considered as the effective particle size which indicates the size of grains below which 10% particles by weight are finer and 90% particles are coarser than D_{10} . Likewise, D_{60} is the size of the sand grain below which 40% of the sample has coarser grains and 60% of the sample has finer grains similarly with D_{30} represents the size of the sand grain below which 30% fine and 70% coarse sand grains are available. D_{10} , D_{30} and D_{60} are assimilated from grade curve.

12.4 Parameters for Gradation

The uniformity-coefficient (C_u) and the gradation coefficient (C_c) are the indicators of gradation of any soil. These indicators aid to categorize the sample either as well or poorly graded. If C_u is the range 4 to 6 then the sample is considered as well-graded. If < 4 , poor-graded and uniform-graded samle has value 1. From the graph drawn between percentage of fines and grain size, the D_{10} , D_{30} , D_{60} , C_u and C_c values were find out from the plotted gradation curve. Uniformity and curvature coefficients are assesses using formulae-

$$C_u = D_{60} / D_{10}$$

$$C_c = (D_{30})^2 / D_{60} \times D_{10}$$

The uniformity-coefficient, curvature-coefficient and the effective size (D_{10}) describe a exact nature of sample. Upper value of C_u shows that the soil sample contains grains with variable sizes.

Table 2. Sieve Analysis data of the samples procured

Sand Sample	Grain size between 4.75 mm and 2.00 mm (% by weight)	Grain size between 2.00 mm and 0.425 mm (% by weight)	Grain size between 0.425 mm and 0.075 mm (% by weight)	D ₁₀ (particle size of grains in mm below that size 10% of the sample are finer and 90% are coarser)	D ₃₀ (particle size of grains in mm below that size 30% of the sample are finer and 70% are coarser)	D ₆₀ (particle size of grains in mm below that size 60% of the sample are finer and 30% are coarser)	Uniformity Coefficient (Cu)	Curvature Coefficient (Cc)
Coarse Sand	17	60	23	0.174	0.433	1.113	6.40	0.97
Fine sand	5	40	55	0.078	0.194	0.482	6.12	1.00

13 Preparation of Sand Columns

Preparation of coarse and fine sand column samples were made by the stuffing sand into poly-vinyl chloride (PVC) tubes of 180 mm height x 45 mm diameter. The dry densities is about 13.9 kN/m³ for sand samples. For permeability test, *Sporosarcina pasteurii* bacterium of different cell count suspended in nutrients were permitted to flow through samples and percolation method is used for unconfined compression strength.

14 Permeability

The permeability of coarse and fine sand samples were evaluated using constant head permeability test as per IS: 2720) – 1986(Part 17).

15 Unconfined Compression Strength

This test is conducted as per IS: 2710– 1986 (Part 10) to determine the shear capacity of the sand samples.

16 Test Results and Discussions

16.1 Permeability

The results for coefficient of permeability for coarse and fine sand samples when treated with various cell concentrations of *Sporosarcina pasteurii* bacterium establish that bacteriological treatment is very effective on coarse sand samples with mean grain size (D₅₀) = 0.984 mm than fine sand with mean grain size (D₅₀) = 0.242 mm. This is very evident as coefficient of permeability of coarse sand is 3.61x10⁻⁷ cm/s which is less than that of fine sand whose value is 1.13x10⁻⁶ at 10⁵ cell concentration of *Sporosarcina pasteurii* bacterium.

16.2 Unconfined Compression Strength

The outcomes for unconfined compression strength for coarse and fine sand samples when treated with various cell concentrations of *Sporosarcina pasteurii* bacterium establish that bacteriological treatment is very effective on coarse sand samples with mean grain size (D₅₀) = 0.984 mm than fine sand with mean grain size (D₅₀) = 0.242 mm. This is very evident as un-confined compression strength of coarse sand is 3.14 MPa which is more than that of fine sand whose value is 2.89 MPa at 10⁵ cell concentration of *Sporosarcina pasteurii* bacterium.

Table 3. Permeability of Untreated and Microbially Treated Samples

Sample	D ₅₀ (mm)	Cell Count (cells per ml)	Coefficient of permeability (cm/sec)	
			Before Treatment	After Treatment
Coarse Sand	0.984	10 ³	1.55x10 ⁻²	0.31x10 ⁻⁷
		10 ⁴	1.55x10 ⁻²	0.50x10 ⁻⁷
		10 ⁵	1.55x10 ⁻²	0.61x10 ⁻⁷
		10 ⁶	1.55x10 ⁻²	0.45x10 ⁻⁷
		10 ⁷	1.55x10 ⁻²	0.44x10 ⁻⁷
Fine Sand	0.242	10 ³	1.32x10 ⁻³	0.56x10 ⁻⁶
		10 ⁴	1.32x10 ⁻³	0.82x10 ⁻⁶
		10 ⁵	1.32x10 ⁻³	1.13x10 ⁻⁶
		10 ⁶	1.32x10 ⁻³	0.78x10 ⁻⁶
		10 ⁷	1.32x10 ⁻³	0.55x10 ⁻⁶

From the permeability coefficients of samples treated with and without bacteria suggest that the coarse sand having size between 4.75 mm to 2.00 mm has less permeability than fine sand with size between 0.0425 mm and 0.0075 mm. In fine sand, the high viscous bacterial suspension cannot pass through the sample so that effective bio-mineralization is prevented from happening due to restricted spaces between soil grains. The optimum cell concentration is chosen where

permeability is very low and being which permeability increases due to turbid bacterial suspension. As concentration increases turbidity of bacterial solution also increases due to formation of suspended organic matter in the bacterial solution. This matter prevents the solution to seep through the sand matrix for the bio-mineralization mechanism to happen. So the bonds developed are very weak and structure has more pathways for permeability.

Table 4. Unconfined Compression Strength of Untreated and *Sporosarcina pasteurii* Treated sand Samples

Sample	D ₅₀ (mm)	Cell Count (cells per ml)	Unconfined Compression Strength (MPa)	
			Distilled water treated sample	Bacteria + nutrients + Calcium lactate treated sample
Coarse Sand	0.984	10 ³	1.39	1.76
		10 ⁴	1.39	2.81
		10 ⁵	1.39	3.14
		10 ⁶	1.39	2.43
		10 ⁷	1.39	1.99
Fine Sand	0.242	10 ³	2.31	2.64
		10 ⁴	2.31	2.77
		10 ⁵	2.31	2.89
		10 ⁶	2.31	2.56
		10 ⁷	2.31	2.44

Unconfined compressive strength of sand samples treated with and without bacteria suggests that at optimum cell concentration compressive strengths are more. Unconfined compressive strength of coarse sand is 3.14 MPa in coarse

sand treated with bacteria where as in unconfined compressive strength in untreated coarse sand sample is 1.39 MPa, So bacteria treated sand has stiffness nearly 2,3 times more than untreated sample.

17 Conclusions

Bio-mediated sandy soil stabilization using urease enzymatic calcite precipitation is a sustainable solution to solidify sand using the mechanism of bio-mineralization. Test conducted to validate the strength and permeability of sand treated with bacteria revealed the following definite conclusions as presented below-

1. Permeability of coarse sand is significantly reduced than in fine sand after the corresponding samples are treated with nutrients suspended *Sporosarcina pasteurii* bacterial solution.
2. Unconfined Compression Strength of coarse sand is significantly high than that of fine sand after the corresponding samples are treated with nutrients suspended *Sporosarcina pasteurii* bacterial solution.
3. Calcite mineral precipitation due to bacteria is more in coarse sand than in fine sand due to better dispersion of bacterial solution in coarse sand matrix than in fine sand matrix leading to superior manifestation of bio-mineralization phenomena.
4. Calcium lactate is used to supplement the microbial activity and promote incessant urease enzymatic calcite precipitation.
5. Optimum cell concentration of *Sporosarcina pasteurii* bacteria solution is required for stimulating urease activity and for maximum mineral precipitation. Insufficient cell concentration hinders the sufficient calcite mineral precipitation in sand matrix.
6. More than acceptable cell concentration inhibits the growth of bacteria resulting from an alkaline environment produced by urea hydrolysis and also high cell concentration increases the turbidity of the bacterial solution may deter its entry into the sand matrix due to which complete mineral precipitation did not take place and also the dispersion of mineral precipitates in sand matrix is not uniform.

References

1. Cheng, L., Shahin, M.A. and Mujah, D., 2017. Influence of key environmental conditions on microbially induced cementation for soil stabilization. *Journal of Geotechnical and Geoenvironmental Engineering*, 143(1), p.04016083.
2. Mujah, D., Shahin, M.A. and Cheng, L., 2017. State-of-the-art review of biocementation by microbially induced calcite precipitation (MICP) for soil stabilization. *Geomicrobiology Journal*, 34(6), pp.524-537.
3. Forster, S.M., 1990. The role of microorganisms in aggregate formation and soil stabilization: types of aggregation. *Arid Land Research and Management*, 4(2), pp.85-98.
4. Rajagiri A, MN Sandhya, Nawaz S, Suresh Kumar T, *E3S Web of Conferences* 87 01004 (2019)
5. Bibi, S., Oualha, M., Ashfaq, M.Y., Suleiman, M.T. and Zouari, N., 2018. Isolation, differentiation and biodiversity of ureolytic bacteria of Qatari soil and their potential in microbially induced calcite precipitation (MICP) for soil stabilization. *RSC advances*, 8(11), pp.5854-5863.
6. Tummala Suresh Kumar, Kosaraju Satyanarayana, *Materials Today: Proceeding*, 26 (2), 3228-3233, (2020).
7. Harris, R.F., Chesters, G., Allen, O.N. and Attoe, O.J., 1964. Mechanisms involved in soil aggregate stabilization by fungi and bacteria. *Soil Science Society of America Journal*, 28(4), pp.529-532.