

# Alkali ions pre-intercalation and reduced graphene coating of MnO<sub>2</sub> for high-capacity Li-ion battery

<sup>1</sup>Ming Zhang, <sup>2</sup>Junshan Zhao, <sup>1</sup>Zixuan Fang\*, <sup>1</sup>Mengqiang Wu\*\*

<sup>1</sup>School of Materials and Energy, University of Electronic Science and Technology of China, Chengdu 611731, China

<sup>2</sup>College of Optoelectronic Engineering, Chengdu University of Information Technology, Chengdu, 610225, China

**Abstract**—MnO<sub>2</sub> is considered to be a prospective material for lithium-ion batteries anode. However, in practical applications, MnO<sub>2</sub> has shortcomings such as low conductivity, large volume change and high charge transfer resistance, which seriously hinder its commercial application. In this work, MnO<sub>2</sub> are pre-intercalated with various alkali cations (Na<sup>+</sup>, or NH<sub>4</sub><sup>+</sup>) and coating with reduced graphene oxide through electrodeposition which designed for LIBs to improve its electrochemical behavior and understand the effect of cations and coating. It demonstrates that alkali cations can affect the growth morphology and electrochemical performance of MnO<sub>2</sub>, and graphene can improve electrical conductivity. Due to the advantages of its structure, MnO<sub>2</sub>&NH<sub>4</sub><sup>+</sup>@rGO shows high capacity, rate performance (640 mAh g<sup>-1</sup>) and a long lifetime in lithium-ion batteries.

## 1. Introduction

Due to the increasingly prominent energy and greenhouse gas issues, people's demand for energy storage equipment is increasing. Lithium-ion batteries (LIBs) have received widespread attention from people which has been widely used because of its high energy density and a long lifetime during cycles [1–3]. However, the energy density of lithium batteries is gradually unable to meet the growing demand of people. One of the important factors affecting the energy density of batteries is the anode material. One of the most important anode materials is the graphite, which was used for most lithium batteries, but shows a theoretical specific capacity of about 350 mAh g<sup>-1</sup>, this specific capacity is not meet commercialization requirements [4, 5]. MnO<sub>2</sub> is considered a promising material as an anode material for lithium-ion batteries, which due to its high theoretical capacity (1230 mAh g<sup>-1</sup>), abundant Resources, and low oxidation /reduction potential.

However, the practical application of MnO<sub>2</sub> in Li-ion batteries still faces many problems and challenges. MnO<sub>2</sub> is easily soluble in electrolytes and shows low conductivity, which will lead to low material utilization and low mass specific capacity. In addition, some studies have shown that the traditional preparation of MnO<sub>2</sub> electrode usually need conductive agents and adhesives, which not only does not contribute to the electrode

capacity, but also increases the electrode volume. The electrodeposition method has advantages such as rapid synthesis, low cost, and simple operation. And the materials prepared by the electrodeposition method are mostly nanostructures. Many researchers used electrodeposition methods to prepare manganese dioxide, which typically exhibited a higher specific capacitance. However, although manganese dioxide prepared by electrodeposition has high capacitance, its cycling performance is often unsatisfactory due to Jahn-Teller effect. Although many research works were proposed to improve the energy density and lifetime of manganese dioxide electrodes. However, it is often difficult to solve both specific capacity and cycle stability problems simultaneously with simple processes.

Herein, we propose a facile electrodeposition method to enable high capacity MnO<sub>2</sub> anode. MnO<sub>2</sub> are pre-intercalated with various alkali cations (Na<sup>+</sup>, or NH<sub>4</sub><sup>+</sup>) and coating with reduced graphene oxide through electrodeposition which designed for LIBs to improve its rate performance, structural and electrochemical cycling stability and understand the effect of cations and coating.

## 2. Experimental details

All MnO<sub>2</sub> electrodeposition experiments were conducted using electrochemical workstation (CHI 660e), with the Ag/AgCl as the reference, and Ni foam as the working electrode. MnO<sub>2</sub> electrode was prepared in 0.1 M

\*Corresponding email. zixuanfang@uestc.edu.cn

\*\*Corresponding email. mwu@uestc.edu.cn

Manganese acetate solution at a constant potential of 0.7 V last about 1 min.  $\text{MnO}_2\&\text{Na}^+\text{@rGO}$  and  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  were prepared by electrodeposition in a mix solution of 0.06 M  $\text{Mn}(\text{CH}_3\text{COO})_2$  and 1mM  $\text{Na}_2\text{SO}_4$  or  $\text{CH}_3\text{COONH}_4$  at a potential of 0.6 V for 1min firstly. Then,  $\text{MnO}_2\&\text{Na}^+\text{@rGO}$  and  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  were deposited at a constant potential of -1.4 V vs. Ag/AgCl with graphene oxide solution as the precursor [6].

All the structures of  $\text{MnO}_2$  were observed by SEM. Both of the Cyclic Voltammetry (CV) and

Electrochemical Impedance Spectroscopy (EIS) tests were performed using electrochemical workstation (CHI 660e). To estimate the Electrochemical properties of  $\text{MnO}_2$ , CR2032 cells were assembled using Li metal as the anode. All the electrochemical performance of the half cells were estimated with a potential range from 0.01 to 3.0 V using LAND battery system.

### 3. Results and Discussion

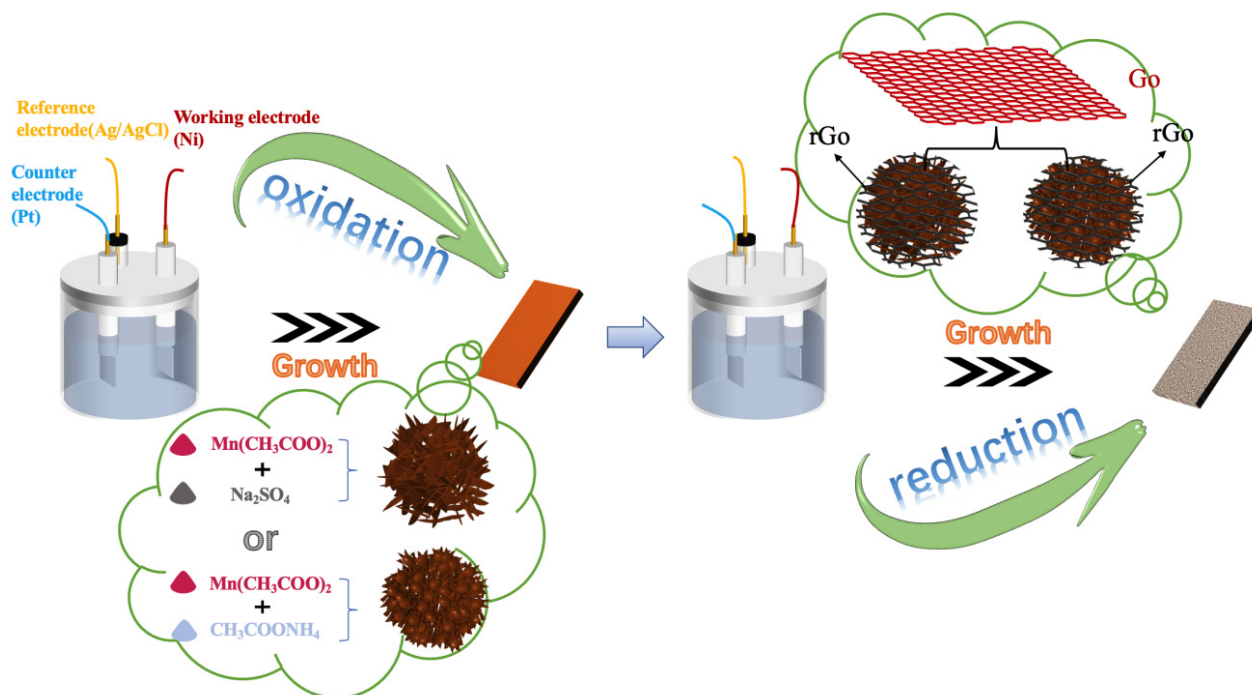


Fig.1 The schematic diagram of  $\text{MnO}_2$  construction

Fig. 1 illustrates our method to synthesize  $\text{MnO}_2$  through a simple electrodeposition method.

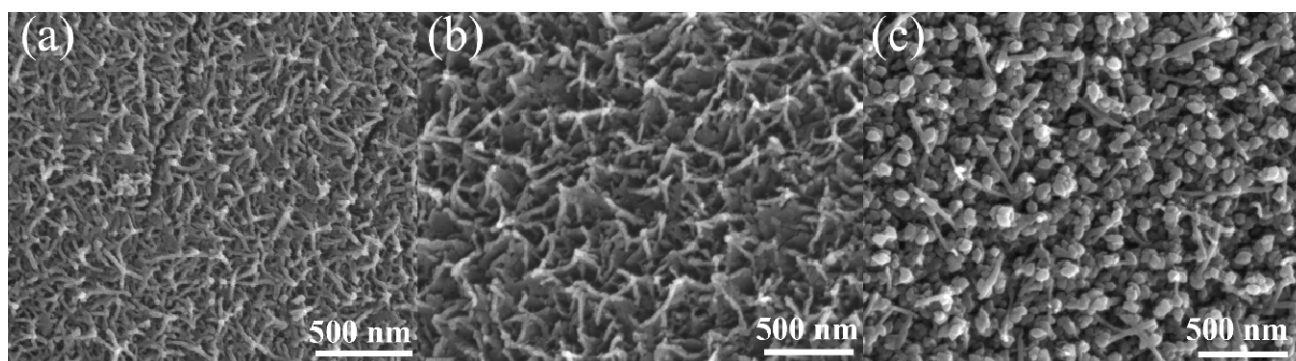


Fig.2 The SEM images. (a) bare  $\text{MnO}_2$ , (b)  $\text{MnO}_2\&\text{Na}^+\text{@rGO}$  and (c)  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$ .

Fig. 2 displays the SEM images of bare  $\text{MnO}_2$ ,  $\text{MnO}_2\&\text{Na}^+\text{@rGO}$  and  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$ . It can be clearly seen that the pre intercalation of cations will significantly change the morphology and structure of  $\text{MnO}_2$ . The surface of bare  $\text{MnO}_2$  is relatively dense,

which is not advantageous to the transmission and electrons move.  $\text{MnO}_2\&\text{Na}^+\text{@rGO}$  shows 3D network structure, interconnected and porous manganese dioxide can increase the contact area with the solution, ensuring rapid electron transmission.  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  exhibits

a fine nanorod structure, which is far from  $\text{MnO}_2$  and  $\text{MnO}_2\&\text{Na}^+\text{@rGO}$ . The structure which with a larger specific surface area is conducive to rapid electron and ion transfer, which is conducive to improving the kinetics of electrochemical reactions. Pre intercalation of Alkali ions can increase the layer spacing of manganese dioxide and broaden the ion channel which is conducive to the improvement of  $\text{MnO}_2$  electrochemistry.

In order to assess the electrochemical properties of all  $\text{MnO}_2$ , CR2032 coin cells were assembled using Li metal as the anode. Fig.3(a) shows the EIS spectrum of different  $\text{MnO}_2$  cells.  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  displays a lower resistance and confirm the effectiveness of the alkali cations pre intercalation and rGO coating. The rate electrochemical performance of different cells is displayed in Fig. 3(b),  $\text{MnO}_2\&\text{Na}^+\text{@rGO}$  and  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  exhibit a high specific capacity than bare  $\text{MnO}_2$ .  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  shows the high capacity of  $640\text{ mAh g}^{-1}$  at  $0.2\text{ A g}^{-1}$ , which is almost 2 times than that of bare  $\text{MnO}_2$  ( $350\text{ mAh g}^{-1}$ ). In addition, even at a high current density of  $5\text{ A g}^{-1}$ ,  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$

exhibits a capacity of about  $300\text{ mAh g}^{-1}$ , bare  $\text{MnO}_2$  shows  $50\text{ mAh g}^{-1}$  only. The good rate performance of  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  proved the superiority of the structure. It is worth noting that in ammonium ions, nitrogen has a strong negative charge, which facilitates the rapid migration and movement of cations in  $\text{MnO}_2$  which can improve the electrochemical performance. However, due to the electrostatic force, Na ions have a certain degree of repulsion with cations. In the subsequent cycles, all cells show an increased specific capacity, which is due to the activation process and generations of some polymers, this phenomenon was observed in many transition metal oxides report [7]. As shown in Fig. 3(c),  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  shows the highest capacity than bare  $\text{MnO}_2$  and  $\text{MnO}_2\&\text{Na}^+\text{@rGO}$ , which is consistent with the pervious analysis. Benefitting from the enhanced electrochemical process,  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  displays a good specific capacity of about  $640\text{ mAh g}^{-1}$  after 200 cycles at the current of  $0.2\text{ A g}^{-1}$ .

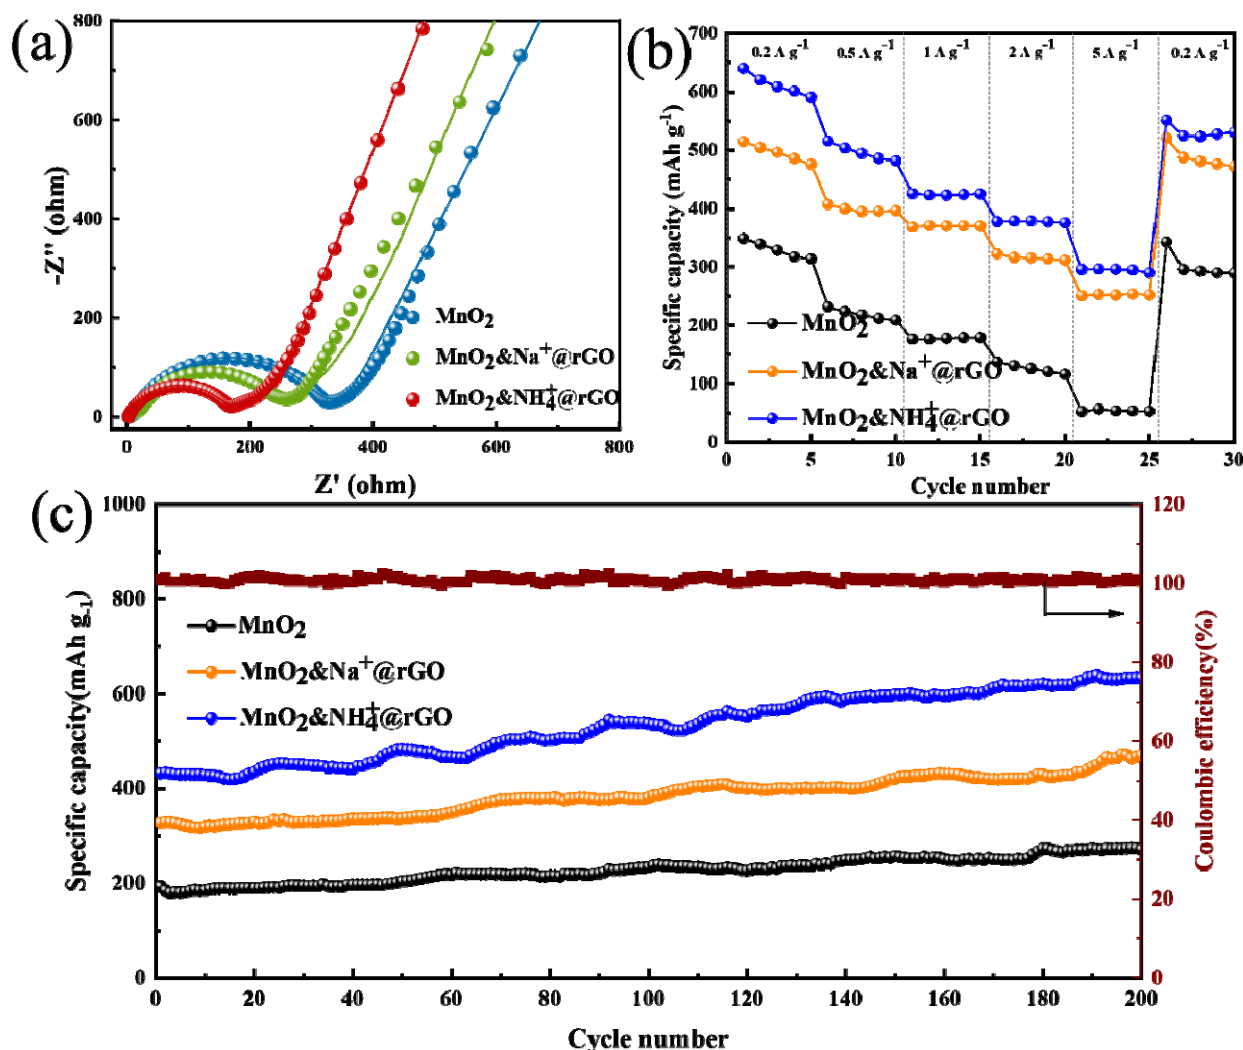


Fig.3 Electrochemical performance of  $\text{MnO}_2$ ,  $\text{MnO}_2\&\text{Na}^+\text{@rGO}$  and  $\text{MnO}_2\&\text{NH}_4^+\text{@rGO}$  cells. (a) EIS spectrum. (b) Rate performance. (c) Cycle performance.

## 4. Conclusion

In summary, MnO<sub>2</sub> are pre-intercalated with various alkali cations (Na<sup>+</sup>, or NH<sub>4</sub><sup>+</sup>) and coating with reduced graphene oxide through electrodeposition which designed for LIBs to improve its electrochemical behavior and understand the effect of cations and coating. SEM results shows that alkali cations can affect the growth morphology of MnO<sub>2</sub>, increase the specific surface area and improve the contact between electrode materials and electrolytes. EIS results shows that pre-intercalated cations and graphene coating can improve the electrical conductivity, lower the charge resistance. Due to the advantages of its structure, MnO<sub>2</sub>&NH<sub>4</sub><sup>+</sup>@rGO shows the highest rate performance (of about 640 mAh g<sup>-1</sup>), and a long cycle lifetime in lithium-ion battery. This work may provide a promising design idea for lithium-ion battery anodes.

## Acknowledgments

This work was financially supported from National Natural Science Foundation of China (Grant No. 52102123), and Natural Science Foundation of Sichuan Province (Grant No. 2022NSFSC2008 and 2022JDRC0080).

## References

1. V. Strong et al., Laser scribing of high-performance and flexible graphene-based electrochemical capacitors, *Science* 335 (2012) 1326–1330.
2. M. Zhang et al., Ultrasonic and NH<sub>4</sub><sup>+</sup> assisted Ni foam substrate oxidation to achieve high performance MnO<sub>2</sub> supercapacitor, *Applied surface science*. 541 (2021) 148546.
3. M. Zhi et al., Nanostructured carbon-metal oxide composite electrodes for supercapacitors: a review, *Nanoscale* 5 (2013) 72–88.
4. X. Gu, L et al., Controlled growth of porous-Fe<sub>2</sub>O<sub>3</sub> branches on b-MnO<sub>2</sub> nanorods for excellent performance in lithium-ion batteries, *Advanced functional materials*. 23 (2013) 4049–4056.
5. L. Suo et al., *Science* 350 (2015) 938.
6. X. Fang et al., Electrode reactions of manganese oxides for secondary lithium batteries, *Electrochem. Commun.* 12 (2010) 1520–1523.
7. M. Zhang et al., High performance MnO<sub>2</sub> supercapacitor material prepared by modified electrodeposition method with different electrodeposition voltages, *Journal of Energy Storage* 29 (2020) 101363.